

Enhancement of the upper critical field by nonmagnetic impurities in dirty two-gap superconductors

A. Gurevich

Applied Superconductivity Center, University of Wisconsin, Madison, Wisconsin 53706

(Dated: February 1, 2008)

Quasiclassic Uzadel equations for two-band superconductors in the dirty limit with the account of both intraband and interband scattering by nonmagnetic impurities are derived for any anisotropic Fermi surface. From these equations the Ginzburg-Landau equations, and the critical temperature T_c are obtained. An equation for the upper critical field, which determines both the temperature dependence of $H_{c2}(T)$ and the orientational dependence of $H_{c2}(\theta)$ as a function of the angle θ between $\mathbf{H}$ and the c-axis is obtained. It is shown that the shape of the $H_{c2}(T)$ curve essentially depends on the ratio of the intraband electron diffusivities D_1 and D_2 , and can be very different from the standard one-gap dirty limit theory. In particular, the value $H_{c2}(0)$ can considerably exceed $0.7T_c dH_{c2}/dT_c$, which can have important consequences for applications of MgB_2 . A scaling relation is proposed which enables one to obtain the angular dependence of $H_{c2}(\theta)$ from the equation for H_{c2} at $\mathbf{H} \parallel c$. It is shown that, depending on the relation between D_1 and D_2 , the ratio of the upper critical field $H_{c2}^{\parallel}/H_{c2}^{\perp}$ for $\mathbf{H} \parallel ab$ and $\mathbf{H} \perp ab$ can both increase and decrease as the temperature decreases. Implications of the obtained results for MgB_2 are discussed.

PACS numbers: PACS numbers: **74.20.De**, **74.20.Hi**, **74.60.-w**

I. INTRODUCTION

Recent discovery of MgB_2 has renewed interest in superconductors with multicomponent order parameters. In particular, extensive ab-initio calculations^{1,2}, along with ample experimental evidences based on STM^{3,4}, point contact⁵, and Raman⁶ spectroscopy, heat capacity⁷ and rf response⁸ measurements strongly indicate that MgB_2 has two distinct s-wave superconducting gaps $\Delta_{\sigma}(0) \approx 7.2\text{mV}$ and $\Delta_{\pi}(0) \approx 2.3\text{mV}$. These gaps reside on different disconnected sheets of the Fermi surface (FS), which comprises nearly cylindrical 2D parts formed by in-plane σ antibonding p_{xy} orbitals of B, and a more isotropic 3D tubular network formed by out-of-plane π bonding and antibonding p_z orbitals of B. So far all attempts to increase the critical temperature T_c of MgB_2 by doping have been unsuccessful⁹. On the other hand, the significant potential of MgB_2 for applications¹⁰ is limited by comparatively low upper critical fields $H_{c2}^{\perp}(0) \simeq 3 - 5T$ and $H_{c2}^{\parallel}(0) \simeq 15 - 19T$ of hexagonal MgB_2 single crystals^{11,12,13,14,15,16,17,18,19,20,21}, where the indices $\perp$ and $\parallel$ correspond to the magnetic field $\mathbf{H}$ perpendicular and parallel to the ab plane, respectively. As far as H_{c2} is concerned, it can be increased by adding nonmagnetic impurities^{22,23}, which are especially effective in the dirty limit, $2\pi k_B T_c < \hbar/\tau$, where τ is the elastic scattering time, $\hbar$ is the Planck constant, and k_B is the Boltzmann constant. In this case, there is a simple universal relation between the zero-temperature value $H_{c2}(0)$, the slope $H'_{c2} = dH_{c2}/dT$ at T_c , and the normal state residual resistivity ρ_n ²²:

$$H_{c2}(0) = 0.69T_c H'_{c2}, \quad H'_{c2} = \frac{4ek_B}{\pi\hbar} N_F \rho_n, \quad (1)$$

where N_F is the density of states at the FS and $-e$ is the electron charge. The fact that adding nonmagnetic impurities increases H_{c2} has been used to significantly improve H_{c2} of $NbTi$ and Nb_3Sn compounds²³. The same approach has been also taken to improve the high-field performance of MgB_2 in which the additional scattering was introduced by proton²⁴ and neutron²⁵ irradiation, and atomic substitutions on both B and Mg sites in thin films²⁶, bulk samples⁹ and wires^{27,28}. For instance, in highly resistive c-axis oriented MgB_2 films²⁶, ρ_n was increased from the nominal value $\sim 1\mu\Omega\text{cm}$ ²⁹ to more than $700\mu\Omega\text{cm}$, which in turn increased the slopes H'_{c2} to rather high values $H'_{c2\perp} \approx 1\text{T/K}$ and $H'_{c2\parallel} \approx 1.8\text{T/K}$, while reducing T_c down to $\approx 30\text{K}$. Based on these numbers, the extrapolation (1) would give the upper critical field, $H_{c2}^{\perp}(0) \approx 20\text{T}$, which is still below $H_{c2}(0) \approx 30\text{T}$ of Nb_3Sn ²³. However, Eq. (1) is a result of the one-gap theory²² which does not take into account the multiple scattering channels in two-gap superconductors. In this paper I show that $H_{c2}(0)$ in two gap superconductors can be significantly higher than what follows from Eq. (1), thus the upper critical fields of MgB_2 alloys can in fact exceed $H_{c2}(0)$ of Nb_3Sn even for the values $H'_{c2\perp} \approx 1\text{T/K}$ which have already been achieved^{26,30}.

The theory of the two-band superconductivity has been developed long ago³¹, and more recently generalized to include the effects of impurities^{32,33,34,35,36,37} and strong electron-phonon coupling^{2,36,37,38}. The Fermi surface of MgB_2 provides three different impurity scattering channels: intraband scattering within each σ and π FS sheets and interband scattering between them. Strong impurity scattering in the dirty limit causes intraband electron diffusion over the respective FS sheets, which reduces the intrinsic anisotropy of Δ_{σ} and Δ_{π} , but does not

affect T_c , in accordance with the Anderson theorem. By contrast, the pairbreaking interband scattering reduces T_c ^{32,33}, but its effect in MgB_2 seems to be not very pronounced due to orthogonality of σ and π orbitals³⁴. It is the multiple scattering channels, which provide the essential flexibility to increase the H_{c2} of MgB_2 to a much greater extent than in one-gap superconductors not only by the usual increase of ρ_n , but also by optimizing the relative weight of the σ and π scattering rates. The latter could be done by selective atomic substitution on B sites (with C, O, etc.) which mostly affect the in-plane σ scattering, and Mg site (Mg vacancies, Al, etc)⁹, which mostly affects out-of-plane π scattering³⁴.

In this work I use a weak coupling multiband BCS model³¹ to develop a theory of magnetic properties of two-gap superconductors in the dirty limit, taking MgB_2 as an example. This approach generalizes the well-known theory developed for dirty one-gap superconductors²². The paper is organized as follows. In section II the quasiclassic Uzadel equations are obtained for an anisotropic two-gap superconductor with the account of both interband and intraband scattering by nonmagnetic impurities. In section III these equations are used to derive the Ginzburg-Landau equations and the critical temperature T_c in the dirty limit. In section IV the linearized Uzadel equations are solved exactly to obtain a general equation for the upper critical field parallel to the c-axis. It is shown that the temperature dependence of $H_{c2}(T)$ can be very different from the one-band theory²², and $H_{c2}(0)$ can be considerably higher than what follows from Eq. (1). In section V I calculate the angular dependence of $H_{c2}(\theta)$ and propose a scaling rule, which shows that the anisotropy ratio $H_{c2}^{\parallel}/H_{c2}^{\perp}$ can both increase and decrease with temperature, depending on the relation between intraband diffusivities. In section VI the results of this work are used to address the observed temperature and orientational dependences of H_{c2} of MgB_2 .

II. UZADEL EQUATIONS

A powerful tool for investigating inhomogeneous states of superconductors is the quasiclassic Eilenberger equations^{39,40} for the Green functions $f(\mathbf{k}, \mathbf{r}, \omega)$, $f^+(\mathbf{k}, \mathbf{r}, \omega)$, $g(\mathbf{k}, \mathbf{r}, \omega)$ and the order parameters $\Delta(\mathbf{k}, \mathbf{r})$ which depend on the coordinates $\mathbf{r}$, the Matsubara frequency $\omega = \pi T(2n + 1)$, and the wave vector $\mathbf{k}$ on the FS (hereafter the units with $k_B = \hbar = 1$ are used). The essential dependence of $f(\mathbf{k}, \mathbf{r}, \omega)$, $g(\mathbf{k}, \mathbf{r}, \omega)$ and $\Delta(\mathbf{k}, \mathbf{r})$ on the direction of $\mathbf{k}$, makes them sensitive to the shape of the FS, which greatly complicates solving the nonlinear Eilenberger equations. Thus, the Eilenberger equations are not so useful in the case of complicated FS, such as the tubular network of disconnected FS sheets of MgB_2 for which the numerical solutions of the Eliashberg equation have shown the significance of the FS anisotropy². However the situation simplifies in the dirty limit for which the impurity scattering within each FS

sheet averages out the angular dependences of $f(\mathbf{k}, \mathbf{r}, \omega)$, $f^+(\mathbf{k}, \mathbf{r}, \omega)$, $g(\mathbf{k}, \mathbf{r}, \omega)$, making them independent of $\mathbf{k}$. In this case the Eilenberger equations reduce to much simpler Uzadel equations⁴¹ in which all microscopic details are hidden in the electronic diffusivity tensors $D_m^{\alpha\beta}$ for each m-th FS sheet and the interband scattering rates $\gamma_{mm'}$ which reflect the underlying FS symmetry⁴².

In this paper I consider a dirty two-gap anisotropic superconductor in the simplest case of two disconnected sheets 1 and 2 of the FS. This model corresponds to the σ and π bands in MgB_2 ^{1,2}, for which the superconducting gaps take the constant values Δ_1 and Δ_2 on the sheets 1 and 2, respectively. The Uzadel equations derived in Appendix A have the form

$$2\omega f_1 - D_1^{\alpha\beta} [g_1 \Pi_\alpha \Pi_\beta f_1 - f_1 \nabla_\alpha \nabla_\beta g_1] = 2\Delta_1 g_1 + \gamma_{12} (g_1 f_2 - g_2 f_1) \quad (2)$$

$$2\omega f_2 - D_2^{\alpha\beta} [g_2 \Pi_\alpha \Pi_\beta f_2 - f_2 \nabla_\alpha \nabla_\beta g_2] = 2\Delta_2 g_2 + \gamma_{21} (g_2 f_1 - g_1 f_2), \quad (3)$$

Eqs. (2) and (3) are supplemented by the self-consistency equations for the order parameters $\Delta_m = |\Delta_m| \exp(i\varphi_m)$:

$$\Delta_m = 2\pi T \sum_{\omega > 0} \sum_m^{\omega_D} \lambda_{mm'} f_{m'}(\mathbf{r}, \omega), \quad (4)$$

normalization condition

$$|f_m|^2 + g_m^2 = 1, \quad (5)$$

and the expression for the supercurrent density

$$J^\alpha = 4\pi i e T \text{Im} \sum_\omega \sum_m N_m D_m^{\alpha\beta} f_m^+ \Pi_\beta f_m. \quad (6)$$

Here the band index m runs from 1 and 2, the functions $f_m(\mathbf{r}, \omega)$ and $g_m(\mathbf{r}, \omega)$ in the m-th band depend on $\mathbf{r}$ and ω but not on $\mathbf{k}$, $D_m^{\alpha\beta}$ are the intraband diffusivity tensors due to nonmagnetic impurity scattering, $\gamma_{mm'}$ are the interband scattering rates, N_m is the partial density of states, $\mathbf{\Pi} = \nabla + 2\pi i \mathbf{A}/\phi_0$, $\mathbf{A}$ is the vector potential, ϕ_0 is the flux quantum, and the summation over the Greek Cartesian indices is implied.

Eqs. (4) contains the matrix of the BCS superconducting coupling constants $\lambda_{mm'} = \lambda_{mm'}^{(ep)} - \mu_{mm'}$, where $\lambda_{mm'}^{(ep)}$ are electron-phonon constants, and $\mu_{mm'}$ is the matrix of the Coulomb pseudopotential. Here the diagonal terms λ_{11} and λ_{22} quantify the intraband superconducting coupling, and off-diagonal terms λ_{12} and λ_{21} describe the interband coupling. The eigenvalues of $\lambda_{mm'}$ are assumed positive, the band 1 having the highest coupling constant λ_{11} . The indices 1 and 2 thus correspond to the σ and π bands of MgB_2 for which *ab-initio* calculations yield $\lambda_{\sigma\sigma} \approx 0.81$, $\lambda_{\pi\pi} \approx 0.285$, $\lambda_{\sigma\pi} \approx 0.119$, and $\lambda_{\pi\sigma} \approx 0.09$ ³⁷. The mixed components λ_{12} and λ_{21} satisfy the symmetry relation³¹ (see also Eq. (A23)):

$$N_1 \lambda_{12} = N_2 \lambda_{21} \quad (7)$$

where N_1 and N_2 are partial densities of states in the bands 1 and 2 ($N_\pi \approx 1.3N_\sigma$ for MgB_2). A similar approach based on the Uzadel equations was recently proposed to describe vortices in two-gap superconductors⁴³.

Formulas for the interband scattering rates $\gamma_{mm'}$ and the intraband diffusivity tensors $D_m^{\alpha\beta}$ expressed in terms of microscopic material parameters are given in Appendix A. They will be used in the next sections as input parameters, which can be either calculated from first principles or extracted from the observed temperature dependences of $H_{c2}(T)$ and resistivity ρ , as discussed below. Here we just emphasize the fact that, although both $D_1^{\alpha\beta}$ and $D_2^{\alpha\beta}$ reflect the underlying symmetry of the FS, the features of atomic orbitals which form the bands 1 and 2 can manifest themselves in very different properties of $D_1^{\alpha\beta}$ and $D_2^{\alpha\beta}$. For instance, the principal value $D_\sigma^{(c)}$ along the c-axis in MgB_2 is much smaller than two principal values $D_\sigma^{(a)}$ and $D_\sigma^{(b)}$ in the ab plane, because of the nearly 2D nature of the σ -band formed by in-plane bonding and antibonding p_{xy} orbitals of B, as was shown by STM³. By contrast, the difference in the principal values $D_\pi^{(c)}$, $D_\pi^{(a)}$ and $D_\pi^{(b)}$ is less pronounced for the 3D π -band formed by the out-of-plane p_z orbitals of B. The resulting relation $D_\sigma^{(c)}/D_\sigma^{(a)} \ll D_\pi^{(c)}/D_\pi^{(a)}$ can manifest itself in anomalous temperature dependence of the anisotropy of H_{c2} , as shown in the next sections.

III. CRITICAL TEMPERATURE AND GINZBURG-LANDAU EQUATIONS

The necessity to satisfy the self-consistency condition (4) complicates solving the nonlinear Eqs. (2)-(3) for inhomogeneous $\Delta_m(\mathbf{r})$. The situation simplifies near T_c where Eqs. (2)-(4) reduce to the Ginzburg-Landau (GL) equations for the order parameters Δ_m . We derive the GL equations neglecting the interband scattering terms $\gamma_{12} \ll \pi T_c$ which are usually small in MgB_2 due to orthogonality of the σ and π orbitals³⁴. Expanding the solution of Eqs. (2) and (3) in powers of Δ_m and its spatial derivatives, and using $g_m \simeq 1 - |f_m|^2/2$, we obtain

$$f_m = \frac{\Delta_m}{\omega} + \frac{D_m^{\alpha\beta}}{2\omega^2} \Pi_\alpha \Pi_\beta \Delta_m - \frac{\Delta_m |\Delta_m|^2}{2\omega^3} \quad (8)$$

Inserting Eqs. (8) into Eq. (4) and summing up over ω , results in the following equations

$$\Delta_1 = \lambda_{11} R_1 + \lambda_{12} R_2, \quad (9)$$

$$\Delta_2 = \lambda_{21} R_1 + \lambda_{22} R_2, \quad (10)$$

$$R_m = \Delta_m l + \frac{\pi D_m^{\alpha\beta}}{8T} \Pi_\alpha \Pi_\beta \Delta_m - \frac{7\zeta(3)}{8\pi^2 T^2} |\Delta_m|^2 \Delta_m, \quad (11)$$

where $R_m = \sum_\omega f_m$, $l = \ln(2\gamma\omega_D/\pi T)$, $\ln \gamma = -0.577$ is the Euler constant, and $\zeta(3) = 1.202$. The supercurrent density at $T - T_c \ll T_c$ is obtained by inserting the first

term in the right hand side of Eq. (44) into Eq. (6) and summing up over ω :

$$J^\alpha = -\frac{\pi e}{4T} \text{Im} \sum_m N_m D_m^{\alpha\beta} \Delta_m^* \Pi_\beta \Delta_m, \quad (12)$$

where the asterisk means complex conjugation. As follows from Eq. (12), the current density near T_c is a sum of independent intraband contributions.

Equilibrium equations (9)-(10) for the order parameters Δ_m are not yet the GL equations which are obtained by varying the free energy functional, $\delta F/\delta \Delta^* = 0$. The reason is that the off-diagonal terms with respect to the band index m in Eqs. (9)-(10) violate the necessary symmetry conditions which the variational equations $\delta F/\delta \Delta^* = 0$ must satisfy. To find the proper linear combinations of Eqs. (9) and (10) which satisfy all necessary symmetry conditions, we first solve Eqs. (9)-(11) for the quantities $N_1 R_1 = (\lambda_{22} \Delta_1 - \lambda_{12} \Delta_2) N_1/w$ and $N_2 R_2 = (\lambda_{11} \Delta_2 - \lambda_{21} \Delta_1) N_2/w$, where $w = \lambda_{11} \lambda_{22} - \lambda_{12} \lambda_{21}$ is the determinant of the matrix $\lambda_{mm'}$. Expressing then R_m via Δ_m using Eq. (11), we obtain the GL equations for an anisotropic two-band superconductor:

$$-a_1 \Delta_1 + b_1 \Delta_1 |\Delta_1|^2 + c_1^{\alpha\beta} \Pi_\alpha \Pi_\beta \Delta_1 + g \Delta_2 = 0, \quad (13)$$

$$-a_2 \Delta_2 + b_2 \Delta_2 |\Delta_2|^2 + c_2^{\alpha\beta} \Pi_\alpha \Pi_\beta \Delta_2 + g \Delta_1 = 0. \quad (14)$$

Here the GL expansion coefficients are given by

$$a_1 = \left(\ln \frac{2\gamma\omega_D}{\pi T} - \frac{\lambda_{22}}{w} \right) N_1, \quad b_1 = \frac{7\zeta(3)N_1}{8\pi^2 T^2}, \quad (15)$$

$$a_2 = \left(\ln \frac{2\gamma\omega_D}{\pi T} - \frac{\lambda_{11}}{w} \right) N_2, \quad b_2 = \frac{7\zeta(3)N_2}{8\pi^2 T^2}, \quad (16)$$

$$c_1^{\alpha\beta} = \pi N_1 D_1^{\alpha\beta}/8T, \quad c_2^{\alpha\beta} = \pi N_2 D_2^{\alpha\beta}/8T, \quad (17)$$

$$g = \lambda_{21} N_2/w = \lambda_{12} N_1/w. \quad (18)$$

The equality in Eq. (18) results from Eq. (7) for the interband coupling constants $\lambda_{12} = V_i N_2$, and $\lambda_{21} = V_i N_1$. The GL equations (13) and (14) can now be obtained by varying the free energy $F = \int [F_1 + F_2 + F_i] dV$, which contains the usual GL intraband contributions

$$F_m = -\frac{a_m}{2} |\Delta_m|^2 + \frac{b_m}{4} |\Delta_m|^4 + \frac{c_m^{\alpha\beta}}{2} \Pi_\alpha \Delta_m \Pi_\beta^* \Delta_m^*, \quad (19)$$

and the interband interaction term

$$F_i = \frac{g}{4} (\Delta_1 \Delta_2^* + \Delta_2 \Delta_1^*). \quad (20)$$

Notice that Eq. (12) for the current density obtained from the Uzadel equations coincides with the general expression $\mathbf{J} = \delta F/\delta \mathbf{A}$, where F is defined by Eqs. (19) and (20). Static GL equations (13)-(20) and their time-dependent generalization⁴⁵ have been suggested phenomenologically to describe various distributions of the order parameter and vortex properties in two-gap superconductors^{44,45}.

Eqs. (13) and (14) give the following equation $a_1 a_2 - g^2 = 0$ for the critical temperature T_c , which results in the quadratic equation for $l_c = \ln(2\gamma\omega_D/\pi T_c)$:

$$1 - \lambda_+ l_c + w l_c^2 = 0 \quad (21)$$

where $\lambda_{\pm} = \lambda_{11} \pm \lambda_{22}$, and $w = \lambda_{11}\lambda_{22} - \lambda_{12}\lambda_{21}$. Solution of Eq. (21) reproduces the well-known result by Suhl, Matthias and Walker³¹:

$$T_{c0} = 1.14\omega_D \exp[-(\lambda_+ - \lambda_0)/2w], \quad (22)$$

where $\lambda_0 = (\lambda_-^2 + 4\lambda_{12}\lambda_{21})^{1/2}$. As follows from Eq. (22), the interband coupling always increases T_c as compared to noninteracting bands ($\lambda_{12} = \lambda_{21} = 0$), while the intraband impurity scattering does not affect T_c , in accordance with the Anderson theorem⁴⁰.

IV. UPPER CRITICAL FIELD FOR $\mathbf{H}_{\parallel c}$

Now we turn to the calculation of the upper critical field H_{c2} applied along the c -axis of a hexagonal crystal. Here H_{c2} is the maximum eigenvalue of the linearized Eqs. (2) and (3) for $f \ll 1$ and $g \rightarrow 1$. In Appendix B, these equations are solved exactly and an equation for H_{c2} is obtained for arbitrary relation between D_1 , D_2 and $\gamma_{mm'}$. This general equation for H_{c2} is very cumbersome, so to make the essential effects of two-gap superconductivity more transparent, I consider here a much simpler case of negligible $\gamma_{mm'}$ for which the nonmagnetic impurity scattering does not affect T_c . If $\gamma_{12} = \gamma_{21} = 0$, the linearized Eqs. (2) and (3) take the form

$$2\omega f_1 - D_1^{\alpha\beta} \Pi_{\alpha} \Pi_{\beta} f_1 = 2\Delta_1, \quad (23)$$

$$2\omega f_2 - D_2^{\alpha\beta} \Pi_{\alpha} \Pi_{\beta} f_2 = 2\Delta_2. \quad (24)$$

For $\mathbf{H}_{\parallel c}$, the relevant solutions of Eqs. (23) and (24) depends only on isotropic in-plane diffusivities, $D_m^{\alpha\beta} = D_m \delta_{\alpha\beta}$. In the gauge $A_y = Hx$ the solutions of Eqs. (4), (23), and (24) are

$$f_m(x, \omega) = \Delta_m(x)/(\omega + \pi H D_m/\phi_0), \quad (25)$$

$$\Delta_m(x) = \tilde{\Delta}_m \exp(-\pi H x^2/\phi_0). \quad (26)$$

Inserting Eqs. (25) and (26) into the gap equation (4) yields two linear equations for $\tilde{\Delta}_1$ and $\tilde{\Delta}_2$ in which the summation over ω is performed using the identity

$$2\pi T \sum_{\omega>0} \frac{1}{\omega + \Omega} = \ln \frac{2\gamma\omega_D}{\pi T} - U \left(\frac{\Omega}{2\pi T} \right), \quad (27)$$

$$U(x) = \psi(1/2 + x) + \psi(1/2), \quad (28)$$

where $\psi(x)$ is the di-gamma function. The equations for $\tilde{\Delta}_1$ and $\tilde{\Delta}_2$ become

$$\tilde{\Delta}_1 = \lambda_{11}[l - U(h)]\tilde{\Delta}_1 + \lambda_{12}[l - U(\eta h)]\tilde{\Delta}_2, \quad (29)$$

$$\tilde{\Delta}_2 = \lambda_{22}[l - U(\eta h)]\tilde{\Delta}_2 + \lambda_{21}[l - U(h)]\tilde{\Delta}_1, \quad (30)$$

where $l = \ln(2\gamma\omega_D/\pi T)$, $h = H_{c2}D_1/2\phi_0 T$, and $\eta = D_2/D_1$. The solvability condition of Eqs. (29) and (30) gives an equation for H_{c2} , in which it is convenient to express ω_D via T_c using Eqs. (21) and (22). As a result, the equation for H_{c2} takes the form

$$2a_0[\ln t + U(h)][\ln t + U(\eta h)] + a_2[\ln t + U(\eta h)] + a_1[\ln t + U(h)] = 0. \quad (31)$$

where $a_1 = 1 + \lambda_-/\lambda_0$, $a_2 = 1 - \lambda_-/\lambda_0$, and $a_0 = w/\lambda_0$. For equal diffusivities, $\eta = 1$, Eq. (31) reduces to the equation $\ln t + U(h) = 0$ for H_{c2} in one-gap dirty superconductors²². A somewhat different form of Eq. (31) was recently obtained from the Uzadel equations⁴³.

Shown in Fig. 1 are $H_{c2}(T)$ curves calculated from Eq. (31) for different diffusivity ratios $\eta = D_2/D_1$. One can clearly see the evolution of the temperature dependence of $H_{c2}(T)$ from the dirty-limit one-band behavior at $D_1 = D_2$, to rather different $H_{c2}(T)$ curves which have portions with both upward and downward curvatures for either $D_1 \ll D_2$ and $D_1 \gg D_2$. In the latter two cases, the zero-temperature value $H_{c2}(0)$ can be significantly higher than the one-gap extrapolation (1). To show this, we obtain expressions for $H_{c2}(T)$ near T_c and $T = 0$. For $T \approx T_c$, Eq. (31) can be expanded in small terms $\sim h$, using $U(h) \approx \pi^2 h/2$, and then solving for H_{c2} :

$$H_{c2} = \frac{8\phi_0(T_c - T)}{\pi^2(a_1 D_1 + a_2 D_2)}, \quad (32)$$

For $D_1 = D_2$, Eq. (32) yields the result of the one-band theory, $H_{c2} = 4(T_c - T)\phi_0/\pi^2 D^2$. Furthermore, if $\lambda_{12} = \lambda_{21} = 0$, then $a_1 = 2$ and $a_2 = 0$, thus $H_{c2}(T)4(T_c - T)\phi_0/\pi^2 D_1$ is determined by D_1 for the band with the highest coupling constant λ_{11} . However, if all constants $\lambda_{mm'}$ are finite, but D_1 and D_2 are very different, then H_{c2} is determined by the maximum diffusivity, for example, by $D_2 \ll D_1$ if the scattering in the "weak" band 2 dominates.

The zero-temperature $H_{c2}(0)$ can be obtained using the asymptotic behavior of $U(x) \approx \ln(4\gamma h)$ for $h \rightarrow \infty$. Then all terms proportional to $\ln t$ cancel out, and Eq. (31) reduces to a quadratic equation for $\ln H_{c2}$, whence

$$H_{c2}(0) = \frac{\phi_0 T_c}{2\gamma\sqrt{D_1 D_2}} \exp\left(\frac{g}{2}\right), \quad (33)$$

$$g = \left(\frac{\lambda_0^2}{w^2} + \ln^2 \frac{D_2}{D_1} + \frac{2\lambda_-}{w} \ln \frac{D_2}{D_1} \right)^{1/2} - \frac{\lambda_0}{w}. \quad (34)$$

For $D_1 = D_2$, Eqs. (33)-(34) again yield the result $H_{c2}(0) = \phi_0 T_c/2\gamma D$ of the one-band dirty limit²². However for $D_1 \neq D_2$, Eqs. (31)-(34) predict a significant enhancement of $H_{c2}(0)$ as compared to $H_{c2}(0) = 0.69 H'_{c2} T_c$ for the symmetric case $D_1 = D_2$. Indeed, in the limit of very different diffusivities, we obtain

$$H_{c2}(0) = \frac{\phi_0 T_c}{2\gamma D_2} e^{\frac{\lambda_- - \lambda_0}{2w}}, \quad D_2 \ll D_1 e^{-\frac{\lambda_0}{w}}, \quad (35)$$

$$H_{c2}(0) = \frac{\phi_0 T_c}{2\gamma D_1} e^{\frac{\lambda_- - \lambda_0}{2w}}, \quad D_1 \ll D_2 e^{-\frac{\lambda_0}{w}}. \quad (36)$$

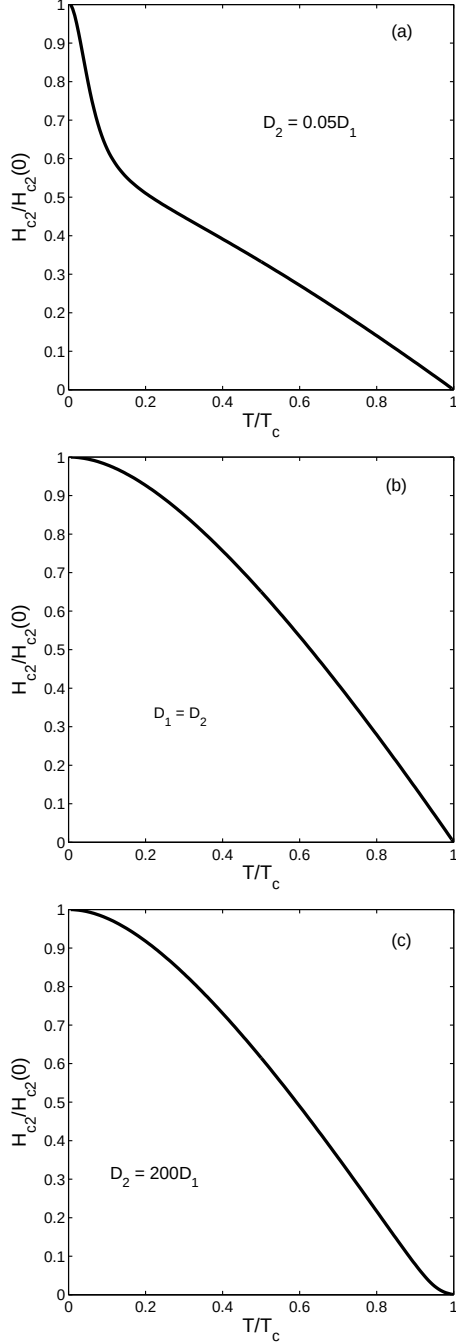


FIG. 1: Temperature dependences $H_{c2}(T)$ calculated from Eq. (31) for different ratios of D_2/D_1 and the coupling constants $\lambda_{\sigma\sigma} \approx 0.81$, $\lambda_{\pi\pi} \approx 0.285$, $\lambda_{\sigma\pi} \approx 0.119$, $\lambda_{\pi\sigma} \approx 0.09$ calculated for MgB_2 ³⁷.

Unlike $H_{c2}(T)$ at $T \approx T_c$, the limiting value of $H_{c2}(0)$ is determined by the *minimum* diffusivity. It is the feature of a two-band superconductor, which causes both the upward curvature and the enhancement of H_{c2} at low T in Fig. 1. In the limit $D_2 \ll D_1$, the diffusivity D_2 does not affect H_{c2} practically for all temperatures $T < T_c$,

except a narrow region $T \ll T_c$, but for $D_2 \rightarrow 0$, the upper critical field $H_{c2}(T)$ diverges at $T = 0$.

V. ANISOTROPY OF H_{c2}

A. General equations

To address the anisotropy of H_{c2} , observed in MgB_2 , we consider a uniaxial crystal in a field $\mathbf{H}$ inclined by the angle θ with respect to the c-axis. Then the tensors $D_{\alpha\beta}$ in Eq. (2)-(3) have two equal principal values $D_m^{(a)}$ in the ab plane and a different value D_m^c along the c-axis. If the z-axis is taken along $\mathbf{H}$ and the a-axis coincides with the y-axis, $D_m^{\alpha\beta}$ has the following nonzero components

$$D_m^{yy} = D_m^{(a)}, \quad (37)$$

$$D_m^{xx} = D_m^{(a)} \cos^2 \theta + D_m^{(c)} \sin^2 \theta, \quad (38)$$

$$D_m^{zz} = D_m^{(c)} \cos^2 \theta + D_m^{(a)} \sin^2 \theta, \quad (39)$$

$$D_m^{xz} = D_m^{(zx)} = (D_m^{(c)} - D_m^{(a)}) \sin \theta \cos \theta \quad (40)$$

In the gauge $A_y = Hx$, the Usadel equations (23) and (24) take the form

$$\begin{aligned} & -D_m^{xx} \partial_{xx} f_m - D_m^{yy} (\partial_y + 2\pi i H x / \phi_0)^2 f_m \\ & - D_m^{zz} \partial_{zz} f_m - 2D_m^{xz} \partial_{xz} f_m + 2\omega f_m = 2\Delta_m \end{aligned} \quad (41)$$

The solution of this equation has the form $f_m(\mathbf{r}) = \exp(ik_z z - ik_z x D_m^{xz} / D_m^{xx} + ik_y y) f_m(x)$, where $f_m(x)$ is determined by the following equation

$$\begin{aligned} & -D_m^{xx} f_m'' + D_m^{yy} (2\pi H x / \phi_0)^2 f_m + 2\omega f_m \\ & + k_z^2 (D_m^{zz} - D_m^{xz2} / D_m^{xx}) f_m = 2\Delta_m, \end{aligned} \quad (42)$$

the prime denotes differentiation over x , and k_y was absorbed by the shift of x ⁴⁶. The upper critical field H_{c2} is the maximum eigenvalue of Eq. (42). Because of the stability condition $D_m^{zz} D_m^{xx} > D_m^{xz2}$, the term quadratic in k_z always decreases the eigenvalues of Eq. (42), so H_{c2} corresponds to $k_z = 0$. In this case the lowest eigenfunction φ_0 of Eq. (42) is

$$\varphi_0^{(m)} \propto e^{-q_m^2 x^2 / 2}, \quad q_m = \left[\frac{2\pi H}{\phi_0} \right]^{1/2} \left[\frac{D_m^{yy}}{D_m^{xx}} \right]^{1/4} \quad (43)$$

An interesting situation occurs if the ratio D_m^{yy} / D_m^{xx} is different for different bands, as characteristic of the σ and π bands of MgB_2 . In this case the solution $f_m(x) \propto \Delta_m(x) \propto \varphi_0(x)$ satisfies Eq. (43), but does not satisfy the self-consistency condition (4), because $q_1 \neq q_2$. This feature of two-gap superconductors can essentially complicate the calculation of H_{c2} for inclined fields, as compared to the case $\mathbf{H} \parallel c$.

$H_{c2}(\theta)$ for an arbitrary field orientation can be obtained by expanding the solution of the inhomogeneous

Eq. (43) in the series of orthogonal normalized eigenfunctions $\varphi_n(q_m x)$ for the different Landau levels n :

$$f_m = \sum_{n=0}^{\infty} \frac{\varphi_n(q_m x)}{\omega + (2n+1)\Omega_m} \int_{-\infty}^{\infty} \Delta_m(u) \varphi_n(q_m u) du, \quad (44)$$

$$\varphi_n(q_m x) = \left(\frac{q_m}{\sqrt{\pi} 2^n n!} \right)^{1/2} e^{-q_m^2 x^2 / 2} H_n(q_m x), \quad (45)$$

$$\Omega_m = (D_m^{xx} D_m^{yy})^{1/2} \pi H / \phi_0, \quad (46)$$

where $H_n(qx)$ is the Hermitian polynomials⁴⁶. Inserting Eq. (45) into Eq. (4) and summing up over ω , gives H_{c2} as the maximum eigenvalue of a matrix $M_{nn'}$, for which the determinant $||M|| = 0$. The matrix $M_{nn'}$ is given by (see Appendix C):

$$M_{nn'} =$$

$$(1 - \lambda_{11} F_n^{(1)}) \delta_{nn'} - \lambda_{12} \lambda_{21} F_{n'}^{(1)} \sum_{s=0}^{\infty} \frac{V_{ns} V_{n's} F_s^{(2)}}{1 - \lambda_{22} F_s^{(2)}}, \quad (47)$$

$$F_n^{(m)} = \ln \frac{2\gamma\omega_D}{\pi T} - \psi \left(\frac{1}{2} + \frac{\Omega_m(2n+1)}{2\pi T} \right) + \psi \left(\frac{1}{2} \right), \quad (48)$$

$$V_{ns} = \int \varphi_n(q_1 x) \varphi_s(q_2 x) dx \quad (49)$$

where $\delta_{nn'}$ is the Kronecker symbol. For $\mathbf{H}||c$ or for equal anisotropy ratios $D_1^{(a)}/D_1^{(c)} = D_2^{(a)}/D_2^{(c)}$, we have $q_1 = q_2$, so $V_{nn'} = \delta_{nn'}$, and all off-diagonal terms of the matrix M vanish. In this case the equation for the maximum eigenvalue H_{c2} is simply $M_{00} = 0$, which reduces to Eq. (31) of the previous paragraph. For arbitrary field orientation and general relations between the coupling constants and the anisotropy ratios $D_m^{(a)}/D_m^{(c)}$ the equation $||M|| = 0$ for H_{c2} can be solved numerically. In this case the matrix $M_{nn'}$ should be first diagonalized to $\tilde{M}_n \delta_{nn'}$, and then H_{c2} can be found as a root of $\tilde{M}_0 = 0$.

The equation for H_{c2} greatly simplifies for the moderate anisotropy characteristic of MgB_2 . To quantify the degree of anisotropy, we introduce the asymmetry parameter $\zeta = [(q_2^2 - q_1^2)/(q_2^2 + q_1^2)]^2$, that is,

$$\zeta = \left[\frac{\sqrt{D_2^{xx}/D_2^{yy}} - \sqrt{D_1^{xx}/D_1^{yy}}}{\sqrt{D_2^{xx}/D_2^{yy}} + \sqrt{D_1^{xx}/D_1^{yy}}} \right]^2 \quad (50)$$

As shown in the next section, the observed anisotropy of H_{c2} of MgB_2 near T_c indicates that $D_2^{(a)} \approx D_2^{(c)}$ and $D_1^{(a)} \approx 4D_1^{(c)}$, $\zeta \approx 1/9$. In this case the matrix elements $V_{0,2s} \propto \zeta^s$ rapidly decreases with s (see Appendix C). By contrast, the factor $F_s^{(2)}/(1 - \lambda_{22} F_s^{(2)})$, which varies much slower with s , can be replaced by its value at $s = 0$ and taken out of the sum. Indeed, near T_c where $\Omega_m \rightarrow 0$, the function $F_s \rightarrow \ln(2\gamma\omega_D/\pi T)$ is independent of s over a very wide range of s , so the above procedure becomes exact. Even for $T = 0$, the function $F \propto \ln[(2s+1)\Omega_m/T_{c0}]$ varies much weaker as compared to the exponential decay of V_{0s}^2 , so the replacement of $F_s^{(2)}/(1 - \lambda_{22} F_s^{(2)})$ by a

constant is still a very good approximation. The remaining summation over s in Eq. (47) can then be performed exactly, using the sum rule due to the orthogonality of the eigenfunctions φ_n (see Appendix C):

$$\sum_{s=0}^{\infty} V_{ns} V_{n's} = \delta_{nn'} \quad (51)$$

Because of the $\delta_{nn'}$ in Eq. (51), all off-diagonal elements of the matrix M vanish, thus the equation $\tilde{M}_{00} = 0$ for H_{c2} takes the form

$$(1 - \lambda_{11} F_0^{(1)})(1 - \lambda_{22} F_0^{(2)}) = \lambda_{12} \lambda_{21} F_0^{(1)} F_0^{(2)} \quad (52)$$

In this equation all $q_m(\theta)$ cancel out, and the anisotropy manifests itself only via $\Omega_m(\theta)$ in the functions $F_0^{(m)}$ defined by Eqs. (46) and (48). After subtraction Eq. (21) for $l_c = \ln(2\gamma\omega_D/\pi T_{c0})$, from Eq. (52), the latter reduces to Eq. (31) if the following rescaling $D_m = (D_m^{xx} D_m^{yy})^{1/2}$ is made. Therefore, all formulas of the previous section can be generalized to the anisotropic case of inclined field by replacing D_1 and D_2 with the angular-dependent diffusivities $D_1(\theta)$ and $D_2(\theta)$ for *both bands*:

$$D_m(\theta) = [D_m^{(a)2} \cos^2 \theta + D_m^{(a)} D_m^{(c)} \sin^2 \theta]^{1/2} \quad (53)$$

For example, Eqs. (31) and (53) give the following angular dependence of $H_{c2}(\theta)$ near T_c :

$$H_{c2}(\theta) = \frac{8\phi_0(T_c - T)}{\pi^2 [a_1 D_1(\theta) + a_2 D_2(\theta)]}, \quad (54)$$

For $D_1 = D_2$, Eq. (54) reduces to the well-known result of the anisotropic GL theory, $H_{c2} = 4\phi_0(T_c - T)/\pi^2 D(\theta)$ for a one-gap superconductor in the dirty limit⁴⁷.

B. Temperature dependence of the anisotropy of H_{c2}

Eqs. (31) and (53) determine both the temperature and angular dependences of H_{c2} . Here the anisotropy of $H_{c2}(\theta)$ essentially depends on both T and the in-plane diffusivity ratio $D_2^{(a)}/D_1^{(a)}$. For instance, let us consider a simpler case of isotropic diffusivity $D_2^{(a)} = D_2^{(c)}$ for the band 2 and anisotropic diffusivity with $D_1^{(a)} \gg D_2^{(c)}$ for the band 1, which qualitatively models the 3D π band and the 2D σ band of MgB_2 . Then for $D_1^{(a)} \gg D_2^{(ab)}$, the angular dependence of H_{c2} is most pronounced at T_c where it is determined by the large anisotropic $D_1(\theta)$ (see Eq. (54), while at lower T the angular dependence of H_{c2} decreases, as it is mostly affected by the nearly isotropic small D_2 (see Eqs. (33)-(36)). However for $D_1^{(a)} \ll D_2^{(a)}$, the situation reverses: the upper critical field is nearly isotropic at T_c , becoming more anisotropic at lower T . These two different types of angular dependencies of $H_{c2}(\theta)$ are shown in Fig. 2.

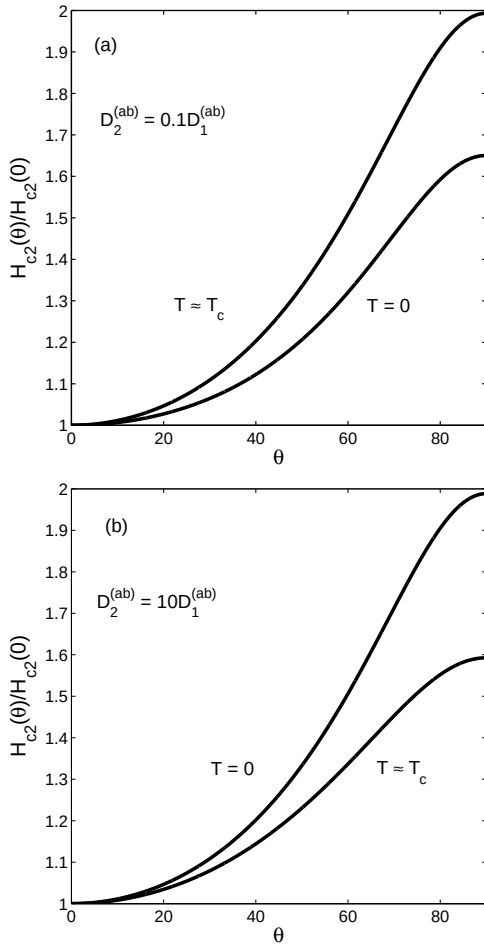


FIG. 2: Angular dependences of $H_{c2}(\theta)$ for $T \approx T_c$ and $T = 0$ calculated from Eq. (54) and Eq. (33), respectively with $D_2^{(c)} = D_2^{(a)}$, $D_1(\theta) = (D_1^{(a)2} \cos^2 \theta + D_1^{(c)} D_1^{(a)} \sin^2 \theta)^{1/2}$ for $D_1^{(a)} = 4D_1^{(c)}$. The cases (a) and (b) correspond to different ratios $D_2^{(a)}/D_1^{(a)}$, and $\lambda_{mm'}$ are the same as for Fig. 1.

The above arguments indicate that the temperature dependence of the anisotropy parameter $H_{c2}^{\parallel}/H_{c2}^{\perp}$ can be rather sensitive to the ratio D_1/D_2 , which in turn is determined by the type of intraband scatterers. Indeed, if the intraband scattering is dominated by impurities (like C or N) which mostly reduce D_1 in the main σ -band, ($D_1 \ll D_2$), then, according to Eqs. (32) and (33), the ratio $H_{c2}^{\parallel}/H_{c2}^{\perp}$ is minimum at T_c and increases as T decreases. This behavior has indeed been observed on many, mostly clean, MgB_2 samples^{11,12,13,14,15,16,17,18,19,20,21}. By contrast, if impurities (like Al, Mg vacancies) cause the strongest intraband scattering in the "weak" π -band, ($D_2 \ll D_1$), then the anisotropy parameter $H_{c2}^{\parallel}/H_{c2}^{\perp}$ would decrease as T decreases. The temperature dependence of $H_{c2}^{\parallel}/H_{c2}^{\perp}$ for these limiting cases is shown in Fig. 3.

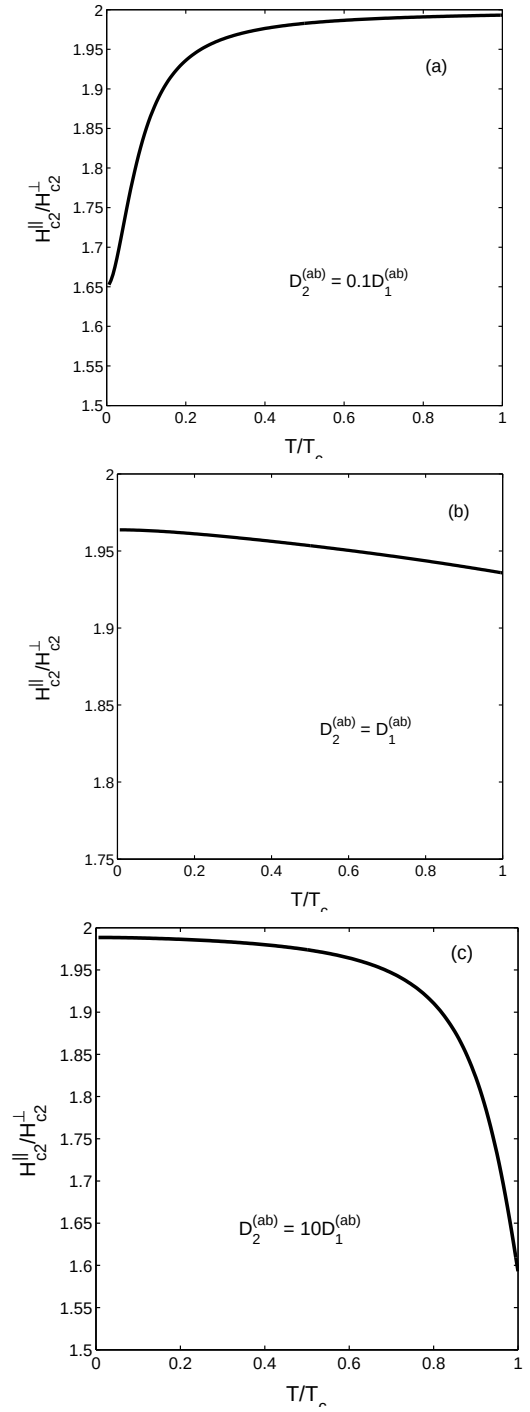


FIG. 3: Temperature dependences of the anisotropy ratio of $H_{c2}^{\parallel}/H_{c2}^{\perp}$ calculated from Eq. (31) with $D_2 = D_2^{(a)}$ and $D_1 = D_1^{(a)}$ for $H_{c2}^{\perp}$, and $D_2 = D_2^{(a)} = D_2^{(c)}$ and $D_1 = \sqrt{D_1^{(c)} D_1^{(a)}}$ with $D_1^{(a)} = 4D_1^{(c)}$ for $H_{c2}^{\parallel}$. The cases (a), (b) and (c) correspond to different ratios $D_2^{(a)}/D_1^{(a)}$, and $\lambda_{mm'}$ are the same as for Fig. 1.

VI. DISCUSSION

The results of this work show that the magnetic behavior of two-gap superconductors can essentially depend on the intraband diffusivity ratio $\eta = D_2^{(a)}/D_1^{(a)}$. This fact can have important consequences for MgB_2 for which H_{c2} can be increased to a much greater extent than in one-band superconductors not just by the usual increase of ρ_n , but also by tuning the ratio of intraband scattering rates via selective atomic substitutions on both Mg and B sites. Actually, this possibility is naturally provided by the electron structure of MgB_2 for which substitutions on Mg site mostly disturb the out-of-plane p_z orbitals of B thus increasing the π scattering. Likewise, atomic substitutions on the B sites mostly increase scattering in the 2D σ band. As shown above, the upward curvature of $H_{c2}(T)$ for $D_2^{(a)} \ll D_1^{(a)}$ can make the zero-temperature $H_{c2}(0)$ significantly higher than what the one-gap estimate (1) suggests. For example, if $D_\pi = 0.05D_\sigma$ as in Fig. 1a, the field $H_{c2}(0) \approx 2.3T_c H'_{c2}$ could approach the paramagnetic limit of MgB_2 , $\simeq 70T$ for the values $H'_{c2} \approx 1T/K$ and $T_c \approx 30K$ observed on dirty c-axis oriented MgB_2 films²⁶. In fact, recent high-field measurements on this film gave $H_{c2}^\perp \approx 33.5T$ and $H_{c2}^\parallel \approx 48T$ which corresponds $D_\pi \approx 0.12D_\sigma$ ³⁰. Thus, dirty MgB_2 can exhibit upper critical fields significantly higher than $H_{c2}(0) \approx 30T$ of Nb_2Sn ²³, which can be very important for applications¹⁰.

The intraband diffusivities D_1 and D_2 can be either calculated from first principles using Eqs. (A22), or extracted from measurements of H_{c2} and ρ_n . For negligible interband scattering, D_1 and D_2 can be obtained using Eq. (32) for H'_{c2} and the relation between intraband diffusivities and the residual conductivity $\sigma = 1/\rho_n$:

$$\sigma_{\alpha\beta} = e^2 \sum_m N_m D_m^{\alpha\beta} \quad (55)$$

For $\mathbf{H} \parallel c$, solving two linear equations (32) and (55) expresses D_1 and D_2 in terms of observed H'_{c2} and ρ_n :

$$D_1 = \frac{1}{a_1 N_2 - a_2 N_1} \left(\frac{8k_B \phi_0 N_2}{\pi^2 \hbar H'_{c2}} - \frac{a_2}{e^2 \rho_n} \right), \quad (56)$$

$$D_2 = \frac{1}{a_1 N_2 - a_2 N_1} \left(\frac{a_1}{e^2 \rho_n} - \frac{8k_B \phi_0 N_1}{\pi^2 \hbar H'_{c2}} \right), \quad (57)$$

where the normal units are restored.

Using the results of *ab-initio* calculations^{34,37} for MgB_2 , $\lambda_{\sigma\sigma} \approx 0.81$, $\lambda_{\pi\pi} \approx 0.285$, $\lambda_{\sigma\pi} \approx 0.119$, $\lambda_{\pi\sigma} \approx 0.09$, $N_\sigma \approx 0.3$ states/cell eV, and $N_\pi \approx 0.41$ states/cell eV, we obtain $\lambda_- = \lambda_{\sigma\sigma} - \lambda_{\pi\pi} = 0.525$, $\lambda_0 = (\lambda_-^2 + 4\lambda_{\pi\sigma}\lambda_{\sigma\pi})^{1/2} = 0.564$, thus $a_1 = 1 + \lambda_-/\lambda_0 = 1.93$, $a_2 = 1 - \lambda_-/\lambda_0 = 0.07$, and $a_1 N_2 \gg a_2 N_1$. Since both D_1 and D_2 must be positive, the slope B'_{c2} for a given ρ_n is confined within the following limits

$$\frac{8ek_B}{\pi a_1} N_1 \rho_n < B'_{c2} < \frac{8ek_B}{\pi a_2} N_2 \rho_n. \quad (58)$$

For negligible interband coupling $a_2 \rightarrow 0$, Eq. (56) reduces to the second Eq. (1), of the one-gap theory, whereas the stability condition (58) requires that B'_{c2} cannot be smaller than $4ek_B N_1 \rho_n / \pi$. This condition gives $B'_{c2} > 0.6T/K$ for $\rho_n = 1m\Omega\text{cm}$, and $N_1 = 0.3$ states/cell eV³⁴, thus $B_{c2}(0)$ for $T_c = 30K$ ²⁶ cannot be smaller than $0.7B'_{c2}T_c = 12.6T$ even for the symmetric case $D_1 = D_2$ which gives the minimum $H_{c2}(0)$ for a given H'_{c2} . For asymmetric case, $D_\pi \ll D_\sigma$ characteristic of dirty c-axis oriented MgB_2 films²⁶, $H_{c2}(0)$ can considerably exceed this minimum³⁰.

Another property for which the diffusivity ratio $D_2^{(a)}/D_1^{(a)}$ is essential is the temperature dependence of the anisotropy of H_{c2} . As shown in the previous section, the anisotropy parameter $H_{c2}^\parallel/H_{c2}^\perp$ increases as T decreases for $D_\sigma \ll D_\pi$, but decreases as T decreases for $D_\sigma \gg D_\pi$ (see Fig. 3). Both cases are in stark contrast with the one-gap theory in which the anisotropy ratio for both the upper critical field $H_{c2}^\parallel/H_{c2}^\perp$ and the lower critical field $H_{c1}^\parallel/H_{c1}^\perp$ is determined by the ratio of the effective masses m_c/m_{ab} and is temperature independent. By contrast, the two-gap MgB_2 exhibits a strong temperature dependence of $H_{c2}^\parallel/H_{c2}^\perp$ which is rather different from the temperature dependence of $H_{c1}^\parallel/H_{c1}^\perp$, as was shown both experimentally and theoretically^{12,35,36}. For the dirty c-axis oriented films, the observed $H_{c2}^\parallel/H_{c2}^\perp$ is about 2²⁶, and $D_\pi \simeq 0.1D_\sigma$ ³⁰. In this case the anisotropy of H_{c2} near T_c is entirely determined by the anisotropy of D_σ , thus from Eq. (54) it follows that $D_\sigma^{(a)} \approx 4D_\sigma^{(c)}$.

VII. ACKNOWLEDGMENTS

This work was supported by the NSF MRSEC (DMR 9214707), and by AFOSR MURI (49620-01-1-0464). I am grateful to D. C. Larbalestier for illuminating discussions.

APPENDIX A: DERIVATION OF THE UZADEL EQUATIONS

We derive the Uzadel equations for an anisotropic two-gap superconductor from the general Eilenberger equations for the quasiclassical Green functions $f(\mathbf{v}, \mathbf{r}, \omega)$, $f^+(\mathbf{v}, \mathbf{r}, \omega)$ and $g(\mathbf{v}, \mathbf{r}, \omega)$ ³⁹

$$(2\omega + \mathbf{v}_k \mathbf{\Pi})f(\mathbf{k}) - 2\Delta g(\mathbf{k}) = n_i \int \frac{dA_{\mathbf{q}}}{v_{\mathbf{q}}} |u_{\mathbf{kq}}|^2 [g(\mathbf{k})f(\mathbf{q}) - f(\mathbf{k})g(\mathbf{q})], \quad (A1)$$

$$(2\omega - \mathbf{v}_k \mathbf{\Pi}^*)f^+(\mathbf{k}) - 2\Delta^* g(\mathbf{k}) = n_i \int \frac{dA_{\mathbf{q}}}{v_{\mathbf{q}}} |u_{\mathbf{kq}}|^2 [g(\mathbf{k})f^+(\mathbf{q}) - f^+(\mathbf{k})g(\mathbf{q})]. \quad (A2)$$

Here $dA_{\mathbf{k}}/v_{\mathbf{k}}$ means integration over the FS with the local density of states $1/v_{\mathbf{k}}$, the integral terms account for

nonmagnetic impurity scattering, $u_{\mathbf{k},\mathbf{q}}$ is the scattering amplitude, n_i is the density of impurities, $\mathbf{v}_{\mathbf{k}}$ is the normal group velocity on an anisotropic FS, the wave vectors $\mathbf{k}$ and $\mathbf{q}$ lie on the FS, and the asterisk means complex conjugate. Eqs. (A1) and (A2) are supplemented by the normalization condition

$$f f^+ + |g|^2 = 1, \quad (\text{A3})$$

the equation for the superconducting gap

$$\Delta(\mathbf{k}, \mathbf{r}) = 2\pi T \sum_{\omega > 0}^{\omega_D} \int \frac{dA_{\mathbf{q}}}{v_{\mathbf{q}}} V(\mathbf{k}, \mathbf{q}) f(\mathbf{q}, \mathbf{r}, \omega), \quad (\text{A4})$$

and the expression for the current density

$$\mathbf{J} = -4\pi T e I m \sum_{\omega > 0}^{\omega_D} \int \frac{dA_{\mathbf{q}}}{v_{\mathbf{q}}} \mathbf{v}_{\mathbf{q}} g(\mathbf{q}, \mathbf{r}, \omega), \quad (\text{A5})$$

where $V(\mathbf{k}, \mathbf{q})$ is the pairing potential.

Now we define the Green functions f_1 and f_2 on two separate sheets of the FS, and write the collision integrals in the right hand side of Eqs. (A1) and (A2) in the form

$$St_1 = n_i \int \frac{dA_{\mathbf{q}_1}}{v_{\mathbf{q}_1}} |u_{\mathbf{k}_1 \mathbf{q}_1}|^2 [g_1(\mathbf{k}_1) f_1(\mathbf{q}_1) - f_1(\mathbf{k}_1) g_1(\mathbf{q}_1)] \\ + n_i \int \frac{dA_{\mathbf{q}_2}}{v_{\mathbf{q}_2}} |u_{\mathbf{k}_1 \mathbf{q}_2}|^2 [g_1(\mathbf{k}_1) f_2(\mathbf{q}_2) - f_1(\mathbf{k}_1) g_2(\mathbf{q}_2)] \quad (\text{A6})$$

$$St_2 = n_i \int \frac{dA_{\mathbf{q}_2}}{v_{\mathbf{q}_2}} |u_{\mathbf{k}_2 \mathbf{q}_2}|^2 [g_2(\mathbf{k}_2) f_2(\mathbf{q}_2) - f_2(\mathbf{k}_2) g_2(\mathbf{q}_2)] \\ + n_i \int \frac{dA_{\mathbf{q}_1}}{v_{\mathbf{q}_1}} |u_{\mathbf{k}_2 \mathbf{q}_1}|^2 [g_2(\mathbf{k}_2) f_1(\mathbf{q}_1) - f_2(\mathbf{k}_2) g_1(\mathbf{q}_1)] \quad (\text{A7})$$

The first integral term in Eqs. (A6) and (A7) describe the *intraband* scattering for which the wave vectors $\mathbf{k}$ and $\mathbf{q}$ lie on the same sheet (1 or 2) of the FS, while the second integral term describes the *interband* scattering for which $\mathbf{k}$ and $\mathbf{q}$ lie on the different FS sheets.

To derive the equations for $f_m(\mathbf{r}, \omega)$, $f_m^+(\mathbf{k}, \omega)$, $g_m(\mathbf{k}, \mathbf{r}, \omega)$, and $\Delta_m(\mathbf{r})$ in the dirty limit, we follow the procedure developed for one-band superconductors, expanding $f(\mathbf{k}, \mathbf{r}, \omega)$ and $g(\mathbf{k}, \mathbf{r}, \omega)$, in spherical harmonics, and keeping only the first dipole term⁴¹

$$f_m(\mathbf{k}, \mathbf{r}, \omega) = f_m(\mathbf{r}, \omega) + (\mathbf{v}_m \delta \mathbf{f}_m(\mathbf{r}, \omega)), \quad (\text{A8})$$

$$g_m(\mathbf{k}, \mathbf{r}, \omega) = g_m(\mathbf{r}, \omega) + (\mathbf{v}_m \delta \mathbf{g}_m(\mathbf{r}, \omega)), \quad (\text{A9})$$

where the band index m runs from 1 to 2, and the last terms in the right hand side describe first order anisotropic corrections to $f(\mathbf{k}, \mathbf{r}, \omega)$ and $g(\mathbf{k}, \mathbf{r}, \omega)$. These corrections are small if $6\pi T_c \gg v_m^2/D_m$, where D_m are intraband diffusivities (see below). The vector corrections $\delta \mathbf{g}_m$ and $\delta \mathbf{f}_m$ are related through the normalization condition (A3):

$$2g_m \delta \mathbf{g}_m = -f_m^+ \delta \mathbf{f}_m - f_m \delta \mathbf{f}_m^+ \quad (\text{A10})$$

Now we insert Eqs. (A8) and (A9) into Eqs. (A1)-(A2) and (A6)-(A7) and integrate over the respective FS sheets: $\int dA_{\mathbf{k}}/v_m(\mathbf{k})$, using $\int \mathbf{v}_m(\mathbf{k}) dA_{\mathbf{k}} = 0$. Since all f_m and $\delta \mathbf{f}_m$ are independent of $\mathbf{v}$, this yields

$$2\omega f_1 - 2\Delta_1 g_1 + r_1^{\alpha\beta} \Pi_{\alpha} \delta f_1^{\beta} = (g_1 f_2 - g_2 f_1) \gamma_{12}, \quad (\text{A11})$$

$$2\omega f_2 - 2\Delta_2 g_2 + r_2^{\alpha\beta} \Pi_{\alpha} \delta f_2^{\beta} = (g_2 f_1 - g_1 f_2) \gamma_{21}, \quad (\text{A12})$$

$$r_m^{\alpha\beta} = \int \frac{v_m^{\alpha}(\mathbf{k}) v_m^{\beta}(\mathbf{k})}{v_m(\mathbf{k}) N_m} dA_{\mathbf{k}} \quad (\text{A13})$$

where $N_m = \int dA_{\mathbf{k}}/v_m(\mathbf{k})$ are partial densities of states, and $\gamma_{mm'}$ are the interband scattering rates⁴²

$$\gamma_{mm'} = \frac{n_i}{N_m} \int \frac{dA_{\mathbf{q}}}{v_m(\mathbf{q})} \frac{dA_{\mathbf{k}}}{v_{m'}(\mathbf{k})} |u_{\mathbf{k},\mathbf{q}}|^2 \quad (\text{A14})$$

Then we substitute Eqs. (A8) and (A9) into Eqs. (A1)-(A2) and (A6)-(A7), multiply them by $\mathbf{v}_m(\mathbf{k})$ and integrate over the respective FS sheets, using the fact that $\int \mathbf{v}_1(\mathbf{k}) \mathbf{v}_2(\mathbf{k}) dA_{\mathbf{k}} = 0$. In the dirty limit, this yields the following relations

$$\Gamma_m^{\alpha\beta} (f_m \delta g_m^{\beta} - g_m \delta f_m^{\beta}) = r_m^{\alpha\beta} \Pi_{\beta} f_m, \quad (\text{A15})$$

$$\Gamma_m^{\alpha\beta} (f_m^+ \delta g_m^{\beta} - g_m \delta f_m^{+\beta}) = -r_m^{\alpha\beta} \Pi_{\beta}^* f_m^+, \quad (\text{A16})$$

Here the tensor $\Gamma_m^{\alpha\beta}$ is defined by

$$\Gamma_m^{\alpha\beta} = \frac{n_i}{N_m} \int \frac{|u_{\mathbf{q},\mathbf{k}}|^2 v_m^{\alpha}(\mathbf{k}) [v_m^{\beta}(\mathbf{k}) - v_m^{\beta}(\mathbf{q})]}{v_m(\mathbf{k}) v_m(\mathbf{q})} dA_{\mathbf{k}} dA_{\mathbf{q}} \quad (\text{A17})$$

Eqs. (A15) and (A16) can be rewritten as

$$f_m \delta g_m^{\alpha} - g_m \delta f_m^{\alpha} = F_m^{\alpha\beta} \Pi_{\beta} f_m, \quad (\text{A18})$$

$$f_m^+ \delta g_m^{\alpha} - g_m \delta f_m^{+\alpha} = -F_m^{\alpha\beta} \Pi_{\beta}^* f_m^+, \quad (\text{A19})$$

where $F_m^{\alpha\beta} = (\Gamma_m^{\alpha\gamma})^{-1} r_m^{\gamma\beta}$. Multiplying Eq. (A18) by f_m^+ and Eq. (A19) by f_m , adding, and then using Eq. (A10), we obtain

$$2\delta g_m^{\alpha} = F_m^{\alpha\beta} (f_m^+ \Pi_{\beta} f_m - f_m \Pi_{\beta}^* f_m^+) \quad (\text{A20})$$

Using Eq. (A15), (A16), (A20), and the normalization condition $g_m^2 + |f_m|^2 = 1$, we obtain

$$\delta f_m^{\alpha} = -F_m^{\alpha\beta} (g_m \Pi_{\beta} f_m - f_m \nabla_{\beta} g_m). \quad (\text{A21})$$

Inserting Eq. (A21) and its conjugate into Eqs. (A11) and (A12), we arrive at Eqs. (2) and (3) in which the intraband diffusivity tensors are given by

$$D_m^{\alpha\beta} = r_m^{\alpha\gamma} (\Gamma_m^{\gamma\mu})^{-1} r_m^{\mu\beta}. \quad (\text{A22})$$

Averaging the gap equation (A4) over the FS, yields Eq. (4) in which the coupling constants $\lambda_{mm'}$ are given by

$$\lambda_{mm'} = \frac{1}{N_m} \int \frac{dA_{\mathbf{k}} dA_{\mathbf{q}}}{v_m(\mathbf{k}) v_{m'}(\mathbf{q})} V(\mathbf{k}, \mathbf{q}), \quad (\text{A23})$$

whence $N_1 \lambda_{12} = N_2 \lambda_{21}$.

APPENDIX B: EQUATIONS FOR H_{c2} AND T_c WITH THE ACCOUNT OF INTERBAND SCATTERING

For $H||c$, the linearized Eqs. (2) and (3) take the form

$$\omega f_1 - \frac{D_1}{2}\Pi^2 f_1 = \Delta_1 + (f_2 - f_1)\gamma_{12}, \quad (\text{B1})$$

$$\omega f_2 - \frac{D_2}{2}\Pi^2 f_2 = \Delta_2 + (f_1 - f_2)\gamma_{21}, \quad (\text{B2})$$

In the gauge $A_y = Hx$, the solution of Eqs. (B1) and (B2) is

$$f_m(x) = \tilde{f}_m e^{-q^2 x^2/2}, \quad \Delta_m(x) = \tilde{\Delta}_m e^{-q^2 x^2/2}. \quad (\text{B3})$$

Here $q^2 = 2\pi H/\phi_0$, and the amplitudes $\tilde{f}_m$ can be expressed via $\tilde{\Delta}_1$ and $\tilde{\Delta}_2$ from Eqs. (B1)-(B3):

$$\tilde{f}_1 = \frac{g_+ \tilde{\Delta}_1 - g_{12} \tilde{\Delta}_2}{\omega + \Omega_+} + \frac{g_- \tilde{\Delta}_1 + g_{12} \tilde{\Delta}_2}{\omega + \Omega_-}, \quad (\text{B4})$$

$$\tilde{f}_2 = \frac{g_- \tilde{\Delta}_2 - g_{21} \tilde{\Delta}_1}{\omega + \Omega_+} + \frac{g_+ \tilde{\Delta}_2 + g_{21} \tilde{\Delta}_1}{\omega + \Omega_-}, \quad (\text{B5})$$

where

$$2\Omega_+ = \omega_+ + \gamma_+ + \Omega_0, \quad 2\Omega_- = \omega_+ + \gamma_+ - \Omega_0, \quad (\text{B6})$$

$$\Omega_0 = (\omega_-^2 + \gamma_+^2 + 2\gamma_- \omega_-)^{1/2}, \quad (\text{B7})$$

$$\gamma_{\pm} = \gamma_{12} \pm \gamma_{21}, \quad \omega_{\pm} = (D_1 \pm D_2)\pi H/\phi_0, \quad (\text{B8})$$

$$2g_{\pm} = 1 \pm \frac{\omega_- + \gamma_-}{\Omega_0}, \quad g_{12} = \frac{\gamma_{12}}{\Omega_0}, \quad g_{21} = \frac{\gamma_{21}}{\Omega_0}. \quad (\text{B9})$$

Inserting Eqs. (B4) and (B5) into Eq. (4) we first sum up over ω , and express the result in terms of the functions

$$F_{\pm} = 2\pi T \sum_{\omega} \frac{1}{\omega + \Omega_{\pm}} = \ln \frac{2\gamma\omega_D}{\pi T} - \psi\left(\frac{1}{2} + \frac{\Omega_{\pm}}{2\pi T}\right) + \psi\left(\frac{1}{2}\right). \quad (\text{B10})$$

Then the self-consistency equations (4) reduce to

$$G_{11}\tilde{\Delta}_1 + G_{12}\tilde{\Delta}_2 = 0, \quad (\text{B11})$$

$$G_{21}\tilde{\Delta}_1 + G_{22}\tilde{\Delta}_2 = 0, \quad (\text{B12})$$

where the matrix $G_{mm'}$ is given by

$$G_{11} = 1 - \lambda_{11}(g_+ F_+ + g_- F_-) + \lambda_{12}g_{21}(F_+ - F_-), \quad (\text{B13})$$

$$G_{12} = \lambda_{11}g_{12}(F_+ - F_-) - \lambda_{12}(g_- F_+ + g_+ F_-), \quad (\text{B14})$$

$$G_{22} = 1 - \lambda_{22}(g_+ F_+ + g_- F_-) + \lambda_{21}g_{12}(F_+ - F_-), \quad (\text{B15})$$

$$G_{21} = \lambda_{22}g_{21}(F_+ - F_-) - \lambda_{21}(g_+ F_+ + g_- F_-). \quad (\text{B16})$$

Using Eqs. (B13)-(B16), the final equation $G_{11}G_{22} - G_{12}G_{21} = 0$ for H_{c2} can be presented in the form

$$1 - \lambda_{11}(g_+ F_+ + g_- F_-) - \lambda_{22}(g_+ F_+ + g_- F_-) + w(g_+ F_+ + g_- F_-)(g_+ F_+ + g_- F_-) + (\lambda_{12}g_{21} + \lambda_{21}g_{12})(F_+ - F_-) = 0, \quad (\text{B17})$$

where H_{c2} is the maximum root of Eq. (B17). Setting $H_{c2} = 0$ in Eq. (B17), gives the equation for T_c with the account of interband scattering for which $\omega_{\pm} = \Omega_{\pm} = 0$, $\Omega_+ = \gamma_{12} + \gamma_{21}$, $g_+ = 2\gamma_{12}/(\gamma_{12} + \gamma_{21})$, $g_- = 2\gamma_{21}/(\gamma_{12} + \gamma_{21})$. Subtracting Eq. (21) for T_{c0} from Eq. (B17), the equation for T_c can be reduced to

$$U\left(\frac{\gamma_{12} + \gamma_{21}}{2\pi T}\right) = \frac{(\lambda_0 - w \ln t) \ln t}{p - w \ln t}, \quad (\text{B18})$$

$$p = \frac{\gamma_{12}(\lambda_1 - 2\lambda_{21}) + \gamma_{21}(\lambda_2 - 2\lambda_{12})}{2(\gamma_{12} + \gamma_{21})}, \quad (\text{B19})$$

where $t = T_c/T_{c0}$, $\lambda_1 = \lambda_0 + \lambda_-$, and $\lambda_2 = \lambda_0 - \lambda_-$. The effect of interband scattering on T_c suppression was considered before^{32,33,35}

APPENDIX C: MATRIX M

Inserting Eq. (44) into the gap equation (4) yields

$$\Delta_m = 2\pi T \sum_{\omega} \sum_{m'} \lambda_{mm'} \sum_{n=0}^{\infty} \frac{\varphi_n(q_{m'}x) C_n^{(m')}}{\omega + (2n+1)\Omega_{m'}}, \quad (\text{C1})$$

where $C_n^{(m)} = \int_{-\infty}^{\infty} \varphi_n(q_m x) \Delta_m(x) dx$. Now we multiply Eq. (C1) by $\varphi_s(q_m x)$, integrate over x using the orthogonality condition $\int \varphi_n(q_m x) \varphi_{n'}(q_m x) dx = \delta_{nn'}$, and then sum up over ω . This gives two sets of linear equations

$$(1 - \lambda_{11} F_s^{(1)}) C_s^{(1)} = \lambda_{12} \sum_n V_{sn} F_n^{(2)} C_n^{(2)}, \quad (\text{C2})$$

$$(1 - \lambda_{22} F_s^{(2)}) C_s^{(2)} = \lambda_{21} \sum_n V_{ns} F_n^{(1)} C_n^{(1)}, \quad (\text{C3})$$

where V_{sn} and $F_n^{(m)}$ are defined as follows

$$V_{sn} = \int_{-\infty}^{\infty} \varphi_s(q_1 x) \varphi_n(q_2 x) dx \quad (\text{C4})$$

$$F_n^{(m)} = \sum_{\omega>0}^{\omega_D} \frac{1}{\omega + (2n+1)\Omega_m} \quad (\text{C5})$$

Eq. (C5) can be expressed in terms of the ψ function as in Eq. (48). Inserting $C_n^{(2)}$ from Eq. (C3) into Eq. (C2) yields the closed set of linear equations for $C_n^{(1)}$

$$\sum_{n'=0}^{\infty} M_{nn'} C_{n'}^{(1)} = 0, \quad (\text{C6})$$

where the matrix $M_{nn'}$ is given by Eq. (47). The solvability condition of Eq. (C6) gives the equation for H_{c2} , which is the maximum eigenvalue of the matrix M .

A general formula for $V_{nn'}$ is rather cumbersome, so to illustrate general behavior of $V_{nn'}$ we consider the case of $n' = 0$ for which the integral (C4) equals⁴⁸

$$V_{n0} = \left(\frac{2q_1 q_2 (2n)!}{2^{2n} (n!)^2 (q_1^2 + q_2^2)} \right)^{1/2} \left(\frac{q_2^2 - q_1^2}{q_2^2 + q_1^2} \right)^n, \quad (\text{C7})$$

if $n = 2s$, and $V_{n0} = 0$ for $n = 2s + 1$, where s is any positive integer. As follows from Eq. (C7), $V_{2s,0} \propto \zeta^s$ exponentially decays with s . The matrix elements $V_{nn'}$ obey the useful sum rule $\sum_{s=0}^{\infty} V_{ns}V_{n's} = \delta_{nn'}$, which can be proven by inserting Eq. (C4) under the sum:

$$\sum_{s=0}^{\infty} \int_{-\infty}^{\infty} dx dx' \varphi_n(q_1 x) \varphi_s(q_2 x) \varphi_{n'}(q_1 x') \varphi_s(q_2 x') \quad (\text{C8})$$

To sum up over s , we use the identity⁴⁶

$$\sum_{s=0}^{\infty} \varphi_s(q_2 x) \varphi_s(q_2 x') = \delta(x - x') \quad (\text{C9})$$

After inserting Eq. (C9) into Eq. (C8), the latter reduces to $\int \varphi_n(q_1 x) \varphi_{n'}(q_1 x) dx$, giving the sum rule (51).

Another equation for H_{c2} valid for weak interband coupling $\lambda_{12}\lambda_{21} \ll \lambda_{11}\lambda_{22}$ and any anisotropy can be obtained as follows. Since off-diagonal terms of M in Eq. (47) are proportional to the small factor $\lambda_{12}\lambda_{21}$, the matrix element $\tilde{M}_0$ can be obtained in the second order perturbation theory:

$$\tilde{M}_0 = M_{00} - \sum_{s=1}^{\infty} \frac{M_{0,2s}M_{2s,0}}{M_{2s,2s}} \quad (\text{C10})$$

Here $M_{0,2s}$ is proportional to the small parameter $\lambda_{12}\lambda_{21}\zeta$, so the sum in Eq. (C10) is by the factor $\sim \lambda_{12}\lambda_{21}\zeta^2$ smaller than the sum in the right hand side of Eq. (47) for M_{00} . Thus, the contribution of the off-diagonal terms to $\tilde{M}_0$ can be neglected, and the equation for H_{c2} is again $M_{00} = 0$, that is,

$$1 - \lambda_{11}F_0^{(1)} = \lambda_{12}\lambda_{21}F_0^{(1)} \sum_{s=0}^{\infty} \frac{V_{0s}^2 F_s^{(2)}}{1 - \lambda_{22}F_s^{(2)}} \quad (\text{C11})$$

For moderate anisotropy ($\zeta \ll 1$), Eq. (C11) reduces to Eq. (52), as the convergence of the sum in Eq. (C11) is due to the rapidly decreasing factor $V_{0s}^2 \propto \zeta^s$. However, for very strong anisotropy $\zeta \approx 1$ at low T when the dependence of $F_s^{(2)}$ on s is essential, Eq. (C11) may be simpler for numerical solution than the full Eq. (C6).

-
- ¹ A. Liu, I.I. Mazin, and J. Kortus, Phys. Rev. Lett. **87** 087005 (2001).
 - ² H.J. Choi, D. Roundy, H. Sun, M.L. Cohen, and S.G. Loule, Nature **418**, 758 (2002); Phys. Rev. B **66**, R020513 (2002).
 - ³ G. Karapetrov, M. Iavarone, W.K. Kwok, G.W. Crabtree, and D.G. Hinks, Phys. Rev. Lett. **86**, 4374 (2001); M. Iavarone, et al. *ibid.* **89**, 1870021 (2002).
 - ⁴ M.R. Eskildsen, M. Kugler, S. Tanaka, J. Jun, S.M. Kazakov, J. Karpinski, and O. Fisher, Phys. Rev. Lett. **89**, 197003 (2002).
 - ⁵ H. Schmidt, J.E. Zasadzinski, K.E. Gray, and D.G. Hinks, D.G. Phys. Rev. Lett. **88**, 1270021-4 (2002).
 - ⁶ X.K. Chen, M.J. Kostantinovic, J.C. Irwin, D.D. Lawrie, and J.P. Franck, Phys. Rev. Lett. **87**, 1570021 (2001).
 - ⁷ F. Bouquet, R.A. Fisher, N.E. Phillips, D.G. Hinks, and J.D. Jorgensen, J.D. Phys. Rev. Lett. **87**, 047001 (2001).
 - ⁸ J.J. Tu, *et al.*, Phys. Rev. Lett. **87**, 277001 (2001); M.-S. Kim, *et al.*, Phys. Rev. B **66**, 0645011 (2002); A.B. Kuz'menko *et al.*, Solid State Comm. **121**, 479 (2002).
 - ⁹ C. Buzea and T. Yamashita, Supercond. Sci. Technol. **14**, R115 (2001).
 - ¹⁰ P. Grant, Nature **411**, 532 (2001); D. Larbalestier, A. Gurevich, D.M. Feldmann, and A. Polyanskii, *ibid.* **414**, 368 (2001).
 - ¹¹ O.F. de Lima, R.A. Ribeiro, M.A. Avila, C.A. Cardoso, and A.A. Coelho, Phys. Rev. Lett. **87**, 047002 (2001).
 - ¹² S.L. Bud'ko, V.G. Kogan, and P.C. Canfield, Phys. Rev. B **64**, 180506 (2001); S.L. Bud'ko and P.C. Canfield, *ibid.*, **65**, 212501 (2002).
 - ¹³ S. Lee, H. Mori, T. Masui, Y. Eltsev, A. Yamamoto, and S. Tajima, J. Phys. Soc. Jap. **70**, 2255 (2001).
 - ¹⁴ A.K. Pradhan, Z.X. Shi, M. Tokunaga, T. Tamegai, Y. Takano, K. Togano, M. Kito, and H. Ihara, Phys. Rev. B **64**, 212509 (2001).
 - ¹⁵ M. Xu, H. Kitazawa, Y. Takano, J. Ye, K. Nishava, H. Abe, A. Matsushita, N. Tsujii and G. Kido, Appl. Phys. Lett. **79**, 2779 (2001).
 - ¹⁶ M. Angst, R. Puzniak, A. Wisiewski, J. Jun, S.M. Kazakov, J. Karpinski, J. Ross, and H. Keller, Phys. Rev. Lett. **88**, 167004 (2002).
 - ¹⁷ A.V. Sologubenko, J. Jun, S.M. Kazakov, J. Karpinski, and H.R. Ott, Phys. Rev. B **65**, 180505 (2002).
 - ¹⁸ K. Takahashi, T. Atsumi, N. Yamamoto, M. Xu, H. Kitazawa, and T. Ishida, Phys. Rev. B **66**, 012501 (2002).
 - ¹⁹ M. Zehetmayer, M. Eisterer, J. Jun, S.M. Kazakov, J. Karpinski, A. Wisniewski, and H.W. Weber, Phys. Rev. B **66**, 052505 (2002).
 - ²⁰ L. Lyard *et al.*, cond-mat/0206231.
 - ²¹ U. Welp *et al.*, cond-mat/0203337.
 - ²² P.G. De Gennes, Phys. Cond. Materie **3**, 79 (1964); N.R. Werthamer, E. Helfand, and P.C. Hohenberg, Phys. Rev. **147**, 295 (1966); K. Maki, *ibid.*, **148**, 362 (1966).
 - ²³ W.A. Fietz and W.W. Webb, Phys. Rev. **161**, 4231 (1967); T.P. Orlando, E.J. McNiff, S. Foner, and M.R. Beasley, Phys. Rev. B **19**, 4545 (1979).
 - ²⁴ G.K. Perkins, G.K., et al. Nature, **411**, 561-563 (2001).
 - ²⁵ M. Eisterer *et al.*, Supercond. Sci. Technol. **15**, L9 (2002); Y. Wang *et al.*, cond-mat/0208169
 - ²⁶ S. Patnaik *et al.*, Supercond. Sci. Technol. **14**, 315 (2001).
 - ²⁷ A. Gümbel, J. Eckert, G. Fuchs, K. Nenkov, K.H. Müller, and L. Schultz, Appl. Phys. Lett. **80**, 2725 (2002).
 - ²⁸ K. Komori, K. Kawagishi, Y. Takano, H. Fujii, S. Arisawa, H. Kumakura, M. Fukutomi, and K. Togano, Appl. Phys.

- Lett. **81**, 1047 (2002).
- ²⁹ D.K. Finnemore, J.L. Ostenson, S.L. Bud'ko, G. Lapertot, and P.C. Canfield, Phys. Rev. Lett. **86**, 2420 (2001).
- ³⁰ A. Gurevich, et al, cond-mat/
- ³¹ H. Suhl, B.T. Matthias, and L.R. Walker, Phys. Rev. Lett. **12**, 552 (1959).
- ³² S.V. Pokrovsky and V.L. Pokrovsky, Phys. Rev. B **54**, 13275 (1996);
- ³³ A.A. Golubov and I.I. Mazin, Phys. Rev. B **55**, 15146 (1997).
- ³⁴ I.I. Mazin *et al.*, Phys. Rev. Lett. **89**, 107002 (2002).
- ³⁵ V.G. Kogan, Phys. Rev. B **66**, R020509 (2002).
- ³⁶ A.A. Golubov, A. Brinkman, O.V. Dolgov, J. Kortus, and O. Jepsen, Phys. Rev. B **66**, 054524 (2002).
- ³⁷ A.A. Golubov, J. Kortus, O.V. Dolgov, O. Jepsen, Y. Kong, O.K. Andersen, B.J. Gibson, K. Ahn, and R.K. Kremer, J. Phys: Condens. Matt. **14**, 1353 (2002).
- ³⁸ S.V. Shulga *et al.*, Phys. Rev. Lett. **80**, 1730 (1998); cond-mat/0103154.
- ³⁹ G. Eilenberger, Z. Phys. **214**, 195 (1969); A.I. Larkin and Yu.N. Ovchinnikov, Zh. Exp. Teor. Fiz. **55**, 2262 (1968) [Sov. Phys. JETP **28**, 1200 (1969)].
- ⁴⁰ J.B. Ketterson and S.N. Song, *Superconductivity* (Cambridge University Press, Cambridge, New York, 1999).
- ⁴¹ K. Uzadel, Phys. Rev. Lett. **25**, 507 (1970).
- ⁴² P.B. Allen, Phys. Rev. B **13**, 1416 (1976).
- ⁴³ A.E. Koshelev and A.A. Golubov, cond-mat/0211388. In this work an equation for H_{c2} equivalent to Eq. (31) divided by $[\ln t + U(h)][\ln t + U(\eta h)]$ was obtained. After such division however this equation does not reproduce the correct result, $\ln t + U(h) = 0$, for $D_1 = D_2$.
- ⁴⁴ Y. Tanaka, Phys. Rev. Lett. **88**, 017002 (2002); E. Babaev *ibid.*, **89**, 067001 (2002).
- ⁴⁵ A. Gurevich and V.M. Vinokur, Phys. Rev. Lett. **90**, ... (2003).
- ⁴⁶ L.D. Landau and E.M. Lifshitz, *Quantum Mechanics*. (Pergamon, New York, 1965).
- ⁴⁷ L.P. Gor'kov and T.K. Melik-Barkhudarov, Sov Phys. JETP **18**, 1031 (1964).
- ⁴⁸ I.S. Gradshteyn and I.M. Ryzhik, *Tables of Integrals, Series, and Products*, (Academic Press, New York, 1980).